

New insight into cuprate charge order from X-ray measurements of $\text{HgBa}_2\text{CuO}_{4+\delta}$

W. Tabis,^{1,2,3,*} B. Yu,² I. Bialo,³ M. Bluschke,^{4,5} T. Kolodziej,^{3,6}
 A. Kozłowski,³ Y. Tang,² E. Weschke,⁴ B. Vignolle,¹ M. Hepting,⁵ H. Gretarsson,⁵
 R. Sutarto,⁷ F. He,⁷ M. Le Tacon,⁸ N. Barišić,^{2,9} G. Yu,² and M. Greven^{2,†}

¹*Laboratoire National des Champs Magnétiques Intenses (CNRS, INSA, UJF, UPS), 31400 Toulouse, France*

²*School of Physics and Astronomy, University of Minnesota, Minneapolis, Minnesota 55455, USA*

³*AGH University of Science and Technology, Faculty of Physics and Applied Computer Science, 30-059 Krakow, Poland*

⁴*Helmholtz-Zentrum Berlin für Materialien und Energie, D-12489 Berlin, Germany*

⁵*Max Planck Institute for Solid State Research, D-70569 Stuttgart, Germany*

⁶*Advanced Photon Source, Argonne National Laboratory, Lemont, IL 60439, USA*

⁷*Canadian Light Source, Saskatoon, Saskatchewan S7N 2V3, Canada*

⁸*Institut für Festkörperphysik, Karlsruher Institut für Technologie, 76021 Karlsruhe, Germany*

⁹*Institute of Solid State Physics, TU Wien, 1040 Vienna, Austria*

(Dated: February 14, 2017)

We present an X-ray scattering study of charge-density-wave (CDW) order in simple tetragonal $\text{HgBa}_2\text{CuO}_{4+\delta}$ (Hg1201). Short-range order appears at a temperature that is distinctly lower than the pseudogap temperature and in excellent agreement with a prior transient reflectivity result. Despite considerable structural differences between Hg1201 and $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$, the CDW correlations exhibit similar doping dependencies, and we demonstrate a universal relationship between CDW wave vector and the size of the reconstructed Fermi pocket observed in quantum oscillation experiments. For Hg1201, this leads us to predict a Lifshitz transition in the CDW-reconstructed state. The CDW correlations in Hg1201 appear to be limited by the disorder potential from unit cells hosting two interstitial oxygen atoms and vanish already below optimal doping, once the correlation length is comparable to the CDW modulation period.

PACS numbers: 61.05.C, 74.25.Dw, 74.72.Jt, 74.62.Dh

The discovery of superconductivity in the lamellar cuprates three decades ago triggered a tremendous amount of scientific activity, yet it has been a challenge to understand the strange-metal (SM) and pseudogap (PG) states from which the superconducting (SC) state evolves upon cooling (Fig. 1) [1]. The extreme cases of zero and high hole-dopant concentrations are well understood: the undoped parent materials are antiferromagnetic (AF) Mott insulators, whereas the highly-doped materials exhibit the characteristics of a conventional Fermi-liquid (FL) metal with a large Fermi surface (FS). The PG phenomenon is associated with myriad ordering tendencies, e.g., translational-symmetry-preserving ($q = 0$) magnetism [2, 3] and a significant enhancement of short-range dynamic AF correlations [4, 5]. Evidence for charge order (in the form of charge-spin “stripes”) was first reported for the La-based cuprates [6]. Subsequent STM [7, 8], NMR [9] and X-ray scattering work [10, 11] found that charge-density-wave (CDW) correlations are a universal characteristic of the underdoped cuprates.

Among the central goals in current cuprate research is to firmly establish the universality and hierarchy of ordering tendencies in the PG state and to shed light on the connection between CDW and SC order. A second goal is to achieve a consistent understanding of CDW-related phenomena observed with distinct probes. A third goal is to establish the connection between CDW order and charge transport. The CDW correlations develop in the part of the phase diagram where FL behav-

ior has been observed [12–15]. Moreover, CDW correlations are thought to be responsible for the FS reconstruction (FSR) implied by low-temperature transport experiments in high magnetic fields [16–21]. Finally, it is essential to understand the role of disorder, which might both stabilize otherwise fluctuating CDW order and limit the spatial extent of CDW domains [22].

Here we tackle these questions through a systematic Cu L -edge resonant X-ray scattering (RXS) study of the doping and temperature dependence of CDW correlations in $\text{HgBa}_2\text{CuO}_{4+\delta}$ (Hg1201). Hg1201 is ideal for experimental study due to its simple tetragonal crystal structure, with only one CuO_2 layer per primitive cell, no intervening CuO chains, and an optimal T_c of nearly 100 K, the highest of all such single-layer compounds. All cuprates exhibit inherent inhomogeneity and disorder [23, 24], and Hg1201 is no exception in this regard [25, 26]. In particular, the interstitial oxygen atoms are likely randomly distributed in the HgO_δ layer ($\delta \approx 0.18$ at optimal doping [27–29]), yet the quasiparticle mean-free path and the screening of the Coulomb repulsion have been estimated to be rather large, which may contribute to the high T_c of Hg1201 [30]. This is supported by the observation of a tiny residual resistivity [12, 31], of Shubnikov-de-Haas oscillations [20, 21], and of Kohler scaling of the magnetoresistance in the PG state [14]. Moreover, Hg1201 features a small density of vortex pinning centers [31], which has enabled the observation of a magnetic vortex lattice [32].

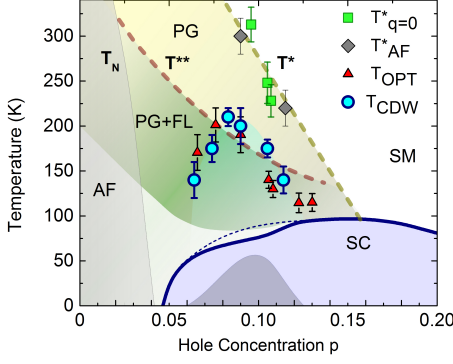


FIG. 1: (color online) Phase diagram of Hg1201 ($p > 0.04$), extended to $p = 0$ based on data for $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$ (YBCO) [12, 36]. Solid blue line: $T_c(p)$ [37]. Dark-grey region: deviation (not to scale) of T_c from estimated parabolic doping dependence (dashed blue line). T^* : PG temperature, estimated from deviation of T -linear planar resistivity in the SM state [12, 15]. T^{**} : temperature below which FL behavior is observed [12–15]. $T_{q=0}$ and T_{AF} : characteristic temperatures below which $q = 0$ magnetic order [3, 38] and an enhancement of AF fluctuations [4, 5] are observed. T_{CDW} : estimated onset of short-range CDW order ($p = 0.09$ result from Ref. [33]). T_{opt} : characteristic temperature observed in time-resolved optical reflectivity measurements [39].

Figure 1 shows the phase diagram of Hg1201, including our new RXS data for the CDW onset temperature (T_{CDW}). Building on prior work for $p \approx 0.09$ ($T_c \approx 72$ K) [33], we study crystals at eight doping levels in the range $0.064 \leq p \leq 0.126$ ($T_c \approx 55 - 94$ K) [34]. The crystals were prepared following established procedures [31, 35]. T_{CDW} is determined for a subset of these samples (Fig. 1) [34]. Except for the most highly doped sample ($T_c \approx 94$ K [34]), a CDW signal is observed at all doping levels (Fig. 2). CDW order is observed at equivalent wave vectors (magnitude q_{CDW}) along [100] and [010], as expected, given the tetragonal structure of Hg1201 [34].

Figure 3 compares the CDW correlation length ξ and peak position q_{CDW} (obtained from Gaussian fits; Fig. 2 [33, 34]) with results for YBCO [40]. The “SC domes” $T_c(p)$ of Hg1201 and YBCO differ somewhat [3, 37], and p should be viewed as an effective concentration [41], yet in both cases the maximum correlation length (ξ_{max}) corresponds to the center of the $T_c(p)$ plateau, where T_{CDW} and the deviation from the interpolated parabolic $T_c(p)$ dependence are the largest (Fig. 1). The suppression of T_c appears to be material specific and stronger in YBCO than in Hg1201 [34]. Whereas the intensity of the CDW peak in Hg1201 saturates in the SC state [34], it decreases below T_c in YBCO (in the absence of an applied magnetic field) [40]. For Hg1201, $\xi_{max}/a \approx 8$, which is about 40% of $\xi_{max}/a \approx 20$ for YBCO [40]. For Hg1201, q_{CDW} is smaller than for YBCO, yet decreases at similar rates with doping (Fig. 3b): -0.6 ± 0.1 and -0.49 ± 0.05 , respectively. The different magnitudes reflect differences in

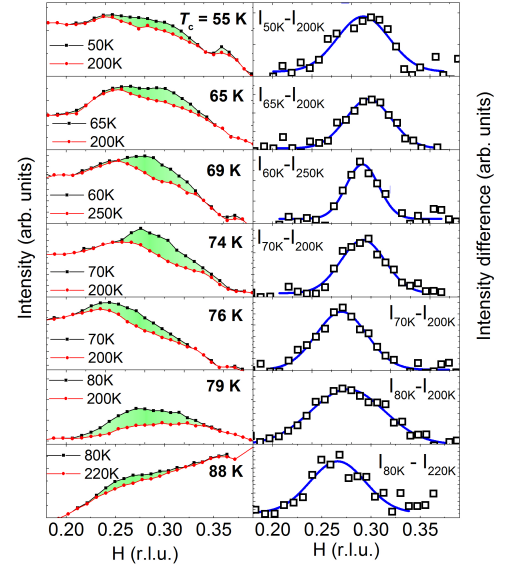


FIG. 2: (color online) Momentum dependence of the CDW peak in seven underdoped samples along [100]. Left: raw RXS spectra collected at indicated temperatures. Right: intensity difference of data in left panels. The high-temperature data constitute an estimate of background scattering [34]. Although the location of the CDW peak is not clear from the raw data, the background-subtracted scans clearly reveal CDW peaks. Blue lines: result of Gaussian fits to the data.

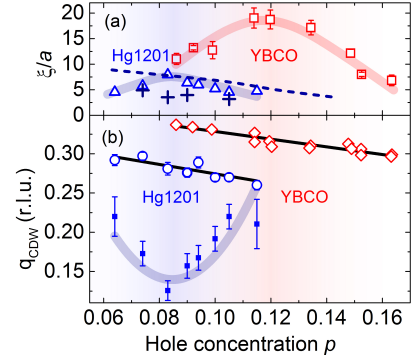


FIG. 3: (color online) (a) CDW correlation length (in units of the planar lattice parameter a) near T_c for Hg1201 (blue triangles; $p = 0.09$ result from Ref. [33]) and YBCO (red squares; Ref. [40]). For Hg1201, ξ/a estimated about 20 K below T_{CDW} is shown as well (blue crosses). Blue dashed line: simulated characteristic size of CDW domains, as discussed in the text. (b) q_{CDW} for Hg1201 (blue circles) and YBCO (red diamonds). Black lines are linear fits. Blue squares indicate a/ξ for Hg1201. The red and blue bands are guides to the eye.

the FS shapes of the two compounds.

There remain numerous open questions regarding the hierarchy of ordering tendencies in the PG state, the correlation between CDW signatures observed with different probes, the connection among CDW order, SC order and charge transport, the connection between the real-

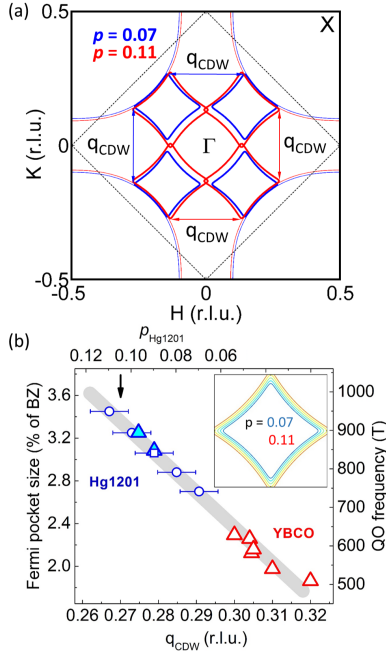


FIG. 4: (color online) (a) Noninteracting tight-binding FS of Hg1201 at $p = 0.07$ (light blue) and $p = 0.11$ (light red) with hopping parameters from Ref. [42]. Thick lines: reconstructed electron pocket; double-arrows: q_{CDW} (see main text). (b) Pocket size, as a fraction of the Brillouin zone (BZ), and associated quantum-oscillation frequency (F) for Hg1201 and YBCO as a function of q_{CDW} . Blue square (Hg1201 [20, 33]) and red triangles (YBCO [43]) represent the doping levels for which both q_{CDW} and F have been determined experimentally. F is related to the Fermi pocket size S via the Onsager relation, $F = \hbar S / 2\pi e$. Blue circles: pocket size estimated from tight-binding calculation, with q_{CDW} obtained from the linear fit in Fig. 3b [34]. Horizontal error bars: experimental uncertainty in q_{CDW} . Blue triangles: recent high-precision experimental result for F [21]. Inset: doping dependence of the electron pocket in the reduced BZ (increments: $\Delta p = 0.01$). Predicted Lifshitz-type change in FS topology at $p \approx 0.105$ (black arrow) due to overlap of reconstructed pockets (see result for $p \approx 0.11$ in (a)).

space charge modulations and the FS topology, and the role of disorder. CDW order appears well below T_{AF} ($T_{AF} \approx T^*$), the temperature below which a distinct enhancement of AF fluctuations is observed [4, 5], consistent with theoretical proposals that AF correlations drive the charge correlations [44–49] and with the notion [15, 33, 50] that PG and CDW formation are distinct phenomena. In Hg1201, the CDW correlations appear at or below T^{**} , the temperature below which FL charge transport is observed [12–14] and below which the Hall constant is nearly independent of temperature, and thus the PG and associated FS is likely fully formed [15]; only at the doping level where CDW order is most robust do T_{CDW} and T^{**} coincide. On the other hand, T_{CDW} coincides at all doping levels with T_{OPT} , the characteristic temperature from transient reflectivity measurements

[39], which suggests that both probes detect the same correlations. At $p \approx 0.12$, ξ becomes comparable to the CDW modulation period (this is also the case at lower doping close to T_{CDW} ; see Fig. 3). Thus, the CDW loses spatial coherence already below optimal doping. Interestingly, a qualitative change in the behavior of the quasiparticle recombination rate (τ_{qp}) was observed at about the same doping level [39]: whereas the behavior of τ_{qp} near optimal doping (where T_{OPT} is not much larger than T_c) is consistent with the mean-field BCS theory of superconductivity, the data at lower doping are best understood upon considering composite SC and CDW fluctuations near T_c . We note that CDW order was reported for optimally-doped ($p \approx 0.16$) Hg1201 [51], yet the very high onset temperature and the values for ξ and q_{CDW} are inconsistent with those extrapolated to optimal doping based on our RXS study [34].

High-precision measurements have demonstrated the existence of a single quantum oscillation (QO) frequency in Hg1201, and hence of a single electron pocket at the Fermi level [20, 21]. This is in stark contrast to orthorhombic double-layer YBCO which, in addition to the main oscillation frequency at ~ 550 T, features satellites at ± 100 T [43] due to magnetic breakdown between the complex electron pockets that originate from a coupling between adjacent CuO_2 layers [52], and additionally a slow frequency (~ 100 T), possibly due to small hole-like FS pockets [53]. Hg1201 thus is a pivotal system to seek a connection between CDW order and FS topology. In Ref. [33], it was demonstrated for Hg1201 ($p = 0.09$) that folding the underlying FS with the measured q_{CDW} , and with assumed biaxial CDW order, results in small electron pockets whose size agrees with the QO frequency observed at the same doping level. Similar agreement was also found for YBCO, but considering only the bonding FS and main QO frequency. Our new result for the doping dependence of q_{CDW} in Hg1201, in combination with a tight-binding FS calculation, allows us to simulate the doping dependence of the electron pocket and to compare with the QO data [20, 21].

Figure 4a shows the tight-binding FS of Hg1201. The electron pockets were constructed by translating the arc-like near-nodal FS parts along $[100]$ and $[010]$ by q_{CDW} estimated from Fig. 3b. Due to the PG in the antinodal regions, no additional hole-pockets are expected in the reconstructed state, consistent with experiment [20, 21]. The resultant relationship between electron pocket size (or, equivalently, QO frequency) and q_{CDW} (and p) is shown in Fig. 4b [34]. The high-precision QO data are in a very good agreement with this prediction [21].

Although our experiment for tetragonal Hg1201 is conducted in the absence of an applied magnetic field and does not allow us to discern whether the short-range CDW order is unidirectional [54] or bidirectional [55], the discussed FSR scenario points to a bidirectional character. X-ray scattering work revealed that orthorhombic

YBCO ($T_c = 67$ K) exhibits three-dimensional (3D) long-range CDW order in fields above ~ 18 T [56], consistent with prior NMR evidence for a field-induced phase transition [9]. This field-induced order is unidirectional and observed only along [010] [56, 57]. NMR work suggests that the 3D order does not simply evolve from the short-range 2D correlations, but rather that the latter coexist with the former [58]. FSR does not necessarily require long-range CDW correlations [21]. Furthermore, FSR by unidirectional (criss-crossed in a bilayer system) order would result in multiple QO frequencies [59], which are not observed in Hg1201 [21]. Although multiple frequencies are observed in YBCO [16], this is not inconsistent with FSR due to bidirectional CDW order [47].

Upon treating the hole concentration as an implicit parameter, a comparison between Hg1201 and YBCO can be made regarding the relationship between q_{CDW} (measured in the absence of a field) and F (estimated for YBCO from the central QO frequency): Fig. 4b demonstrates that these two observables exhibit a universal linear relationship despite the different FS topologies of the two compounds. It is thus reasonable to assume that the CDW order observed in zero field is universally responsible for the reconstruction of the pseudogapped FS.

Our calculation for Hg1201 points to a Lifshitz transition due to overlap of the electron pockets as the hole concentration approaches $p \sim 0.105$ (Fig. 4), resulting in the formation of a hole pocket centered at the BZ center. This transition would significantly alter the electronic properties of Hg1201, with distinct signatures expected in transport experiments in high magnetic fields.

A key question is the influence of disorder on the CDW correlations. It has been suggested that disorder pins otherwise fluctuating CDW correlations and disrupts CDW coherence, rendering ξ finite [22]. This is supported by recent NMR work for YBCO that indicates static correlations pinned by native defects below T_{CDW} , although ξ may indeed be set by the correlation length of the pure system [58]. Alternatively, CDW order might be long-ranged, static and commensurate with the lattice in the absence of disorder [60].

Although we are not able to experimentally distinguish between these scenarios, we can gain new insight from considering the fact that a major source of disorder in Hg1201 are the randomly distributed interstitial oxygen (i-O) atoms in the HgO_δ layers. We have simulated the effects of these i-O atoms on the CDW correlation length [34] and find that the average size of ordered patches pinned (in the form of halos around the pinning centers) or limited by i-O is very small, $\xi/a \approx 1.6$ at $p = 0.09$, whereas the experimental value is $\xi/a \approx 7 - 8$ at low temperatures ($\xi/a \approx 4 - 5$ close to T_{CDW}). This implies that individual i-O atoms have a rather weak effect. However, the local interactions should be more significantly altered by unit cells with two i-O atoms (one in each of the two HgO_δ layers adjacent to a CuO_2 layer).

Indeed, in this case we find that the simulated correlation length agrees rather well with the low-temperature data (Fig. 3a). In this picture, phase decoherence among neighboring CDW patches naturally limits the CDW correlation length in Hg1201 above $p \approx 0.09$. In YBCO, various types of oxygen-dopant defects are observed that may similarly limit ξ/a [61]. Hg1201 exhibits the highest optimal T_c of all single-layer cuprates [24]. It is an intriguing possibility that T_c at optimal doping is so high in part because the disorder potential of i-O pairs disrupts CDW order that would otherwise compete with SC order up to or even beyond optimal doping, as in YBCO or in single-layer electron-doped $\text{Nd}_{2-x}\text{Ce}_x\text{CuO}_{4+\delta}$ [62].

Disorder and electronic inhomogeneity are inherent to the cuprates [23, 24]. NMR measurements indicate that, similar to other cuprates, Hg1201 exhibits a considerable local hole-concentration distribution [26]. As a result, volume-averaging probes (e.g., XRS, optical spectroscopy and charge transport) integrate contributions from local regions with different doping levels around the nominal values. This averaging might mask a possible inherent electronic instability at a distinct doping level where the CDW phenomenon is most robust ($p \approx 0.08$ in Hg1201). On the other hand, if CDW properties evolve monotonically as a function of doping, we expect that inhomogeneity causes little effect (as the averaged properties are effectively represented by the median value).

In summary, our resonant X-ray scattering study of CDW order in simple tetragonal Hg1201 provides new insight into this phenomenon and its connection with charge transport in the cuprates. Although the observed doping and temperature dependencies are similar to YBCO, the structural simplicity of Hg1201 enables us to make a direct link between the normal state and the Fermi-surface-reconstructed state, and to predict a Lifshitz-type transition due to the eventual overlap of the reconstructed electron pockets. The CDW order vanishes at T_{CDW} and already well below optimal doping, once the correlation length is comparable to the CDW modulation period. T_{CDW} as determined with X-rays coincides with the characteristic temperature identified in prior transient reflectivity work. The CDW correlation length in Hg1201 is not set by individual interstitial oxygen dopants, but pairs of such dopants within the same unit cell might set an upper bound on this length.

We thank A. V. Chubukov, M.-H. Julien, Yuan Li, E. H. da Silva Neto, and C. Proust for valuable comments on the manuscript, and acknowledge the contributions of M. K. Chan, C. J. Dorow and M. J. Veit to the sample preparation. The work at the University of Minnesota (crystal growth and characterization, X-ray measurements and data analysis) was funded by the Department of Energy through the University of Minnesota Center for Quantum Materials, under DE-FG02-06ER46275 and DE-SC-0006858. Research performed at the Canadian Light Source, was supported by CFI, NSERC, the University of

Saskatchewan, the Government of Saskatchewan, Western Economic Diversification Canada, NRC, and CIHR. N.B. acknowledges the support of FWF project P27980-N36.

* Electronic address: wojciech.tabis@lncmi.cnrs.fr

† Electronic address: greven@umn.edu

- [1] B. Keimer *et al.*, Nature **518**, 179 (2015).
- [2] B. Fauqué *et al.*, Phys. Rev. Lett. **96**, 197001 (2006).
- [3] Y. Li *et al.*, Nature **455**, 372 (2008).
- [4] M.K. Chan *et al.*, Nat. Commun. **7**, 10819 (2016).
- [5] M.K. Chan *et al.*, Phys. Rev. Lett. **177**, 277002 (2016).
- [6] J. M. Tranquada *et al.*, Nature **375**, 561 (1995).
- [7] J. Hoffman *et al.*, Science **295**, 466 (2002).
- [8] C. Howald, H. Eisaki, N. Kaneko, and A. K. Kapitulnik, Proc. Natl Acad. Sci. USA **100**, 9705 (2003).
- [9] T. Wu *et al.*, Nature **477**, 191 (2011).
- [10] G. Ghiringhelli *et al.*, Science **337**, 821 (2012).
- [11] J. Chang *et al.*, Nat. Phys. **8**, 871 (2012).
- [12] N. Barišić *et al.*, Proc. Nat. Acad. Sci. USA **110**, 12235 (2013).
- [13] S. I. Mirzaei *et al.*, Proc. Nat. Acad. Sci. USA **110**, 5774 (2013).
- [14] M. K. Chan *et al.*, Phys. Rev. Lett. **113**, 177005 (2014).
- [15] N. Barišić *et al.*, arXiv:1507.07885.
- [16] N. Doiron-Leyraud *et al.*, Nature **447**, 565 (2007).
- [17] A. F. Bangura *et al.*, Phys. Rev. Lett. **100**, 047004 (2008).
- [18] D. LeBoeuf *et al.*, Nature **450**, 533 (2007).
- [19] N. Doiron-Leyraud *et al.*, Phys. Rev. X **3**, 021019 (2013).
- [20] N. Barišić *et al.*, Nat. Phys. **9**, 761 (2013).
- [21] M.K. Chan *et al.*, Nat. Commun. **7**, 12244 (2016).
- [22] Y. Caplan, G. Wachtel, and D. Orgad, Phys. Rev. B **92**, 224504 (2015).
- [23] J. C. Phillips, A. Saxena and A. R. Bishop, Rep. Prog. Phys. **66**, 2111 (2003).
- [24] H. Eisaki *et al.*, Phys. Rev. B **69**, 064512 (2004).
- [25] J. Bobroff *et al.*, Phys. Rev. Lett. **78**, 3757 (1997).
- [26] D. Rybicki *et al.*, J. Supercond. Nov. Magn. **22**, 179 (2009).
- [27] A. M. Abakumov *et al.*, Phys. Rev. Lett., **80**, 385 (1998).
- [28] E. V. Antipov, *et al.*, Physica B **241**, 243 (1998).
- [29] S. N. Putilin, *et al.*, Physica C: Supercond. and Its Applic., **338**, 52 (2000).
- [30] W. Chen, G. Khaliullin, and O. P. Sushkov *et al.*, Phys. Rev. B **83**, 064514 (2011).
- [31] N. Barišić *et al.*, Phys. Rev. B **78**, 054518 (2008).
- [32] Y. Li *et al.*, Phys. Rev. B **83**, 054507 (2011).
- [33] W. Tabis *et al.*, Nat. Commun. **5**, 5875 (2014).
- [34] See Supplemental Material for sample information and additional analysis.
- [35] X. Zhao *et al.*, Adv. Mater. **18**, 3243 (2006).
- [36] F. Coneri *et al.*, Phys. Rev. B **81**, 104507 (2010).
- [37] A. Yamamoto *et al.*, Phys. Rev. B **63**, 024504 (2000).
- [38] Y. Li *et al.*, Phys. Rev. B **84**, 224508 (2011).
- [39] J. P. Hinton *et al.*, Scientific Rep. **6**, 23610 (2016).
- [40] S. Blanco-Canosa *et al.*, Phys. Rev. B **90**, 054513 (2014).
- [41] D. Rybicki *et al.*, Nat. Commun. **7**, 11413 (2016).
- [42] T. Das, Phys. Rev. B **86**, 054518 (2012).
- [43] B. Vignolle *et al.*, C. R. Phys. **14**, 39 (2013).
- [44] M. A. Metlitski and S. Sachdev, Phys. Rev. B **82**, 075128 (2010).
- [45] K. B. Efetov, H. Meier, and C. Pépin, Nat. Phys. **9**, 442 (2013).
- [46] Y. Wang and A. V. Chubukov, Phys. Rev. B **90**, 035149 (2014).
- [47] A. Allais, J. Bauer, and S. Sachdev, Phys. Rev. B **90**, 155114 (2014).
- [48] W. A. Atkinson, A. P. Kampf, and S. Bulut, New J. Phys. **17**, 013025 (2015).
- [49] Y. Wang, D. Agterberg, and A. V. Chubukov, Phys. Rev. Lett. (2015).
- [50] S. Badoux *et al.*, Nature **531**, 210 (2016).
- [51] G. Campi *et al.*, Nature **525**, 359 (2015).
- [52] S. Sebastian *et al.*, Phys. Rev. Lett. **108**, 196403 (2012).
- [53] N. Doiron-Leyraud *et al.*, Nat. Commun. **6**, 6034 (2015).
- [54] R. Comin *et al.*, Science **347**, 1335 (2015).
- [55] E. M. Forgan *et al.*, Nat. Commun. **6**, 10064 (2015).
- [56] S. Gerber *et al.*, Science **350**, 949 (2015).
- [57] J. Chang *et al.*, Nat. Commun. **7**, 11494 (2016).
- [58] T. Wu *et al.*, Nat. Commun. **6**, 6438 (2015).
- [59] A.V. Maharaj *et al.*, Phys. Rev. B **93**, 094503 (2016).
- [60] L. Nie *et al.*, Proc. Natl Acad. Sci. USA **111**, 7980 (2014).
- [61] T. Wu *et al.*, Phys. Rev. B **93**, 134518 (2016).
- [62] E. Da Silva Neto *et al.*, Science Adv. **2**, e1600782 (2016).
- [63] D. G. Hawthorn, *et al.*, Rev. Sci. Instrum. **82**, 073104 (2011).
- [64] I. M. Vishik *et al.*, Phys. Rev. B **89**, 195141 (2012).
- [65] N. Harrison and S. E. Sebastian, Phys. Rev. Lett. **106**, 226402 (2011).
- [66] R. Liang *et al.*, Phys. Rev. B **73**, 180505 (2006).

Supplemental Material for “New insight into cuprate charge order from X-ray measurements of $\text{HgBa}_2\text{CuO}_{4+\delta}$ ” (W. Tabis et al.)

Samples. Hg1201 single crystals were grown by a previously reported flux method [35], subsequently annealed to achieve the the desired oxygen (and hence hole) concentration [31], and then quenched to room temperature. The superconducting transition was determined from magnetic susceptibility measurements, and the onset of the diamagnetic response was adopted as the critical temperature T_c . The hole concentration was estimated from the T_c vs. p relationship established for polycrystalline samples [37]. Sample information and some experimental results are summarized in Table I. The typical crystal dimensions were $2 \times 2 \times 0.5 \text{ mm}^3$, with the short side along the c axis. The X-ray penetration length in Hg1201 is about $0.2 \text{ }\mu\text{m}$ at the energy used in the soft X-ray experiment ($\hbar\omega \approx 932 \text{ eV}$). In order to ensure flat and clean surfaces, the samples were polished multiple times with sandpaper with increasingly finer grade, ranging from $1 \text{ }\mu\text{m}$ to $0.05 \text{ }\mu\text{m}$.

Experiments. Resonant X-ray scattering (RXS) measurements at the Cu L_3 edge were performed at the UE46 beam line of the BESSY-II synchrotron in Berlin, Germany, and at the REIXS (Resonant Elastic and Inelastic X-ray Scattering) beam line [63] of the Canadian Light Source. In order to determine the exact resonance energy, X-ray absorption measurements were performed in total-fluorescence-yield configuration. The incident X-ray beam was then tuned to the maximum of the fluorescence signal for each individual sample ($\hbar\omega \approx 932 \text{ eV}$). Since the structure of Hg1201 contains only one Cu site per formula unit, a fluorescence spectrum displays a single maximum. Momentum scans were performed by rotating the sample about the axis perpendicular to the scattering plane, and the detector angle was set to $2\theta = 160^\circ$. In the configuration used in the experiment, K was set to zero, and H was coupled to L during the scans ($\mathbf{Q} = (H, K, L)$). The maximum of the CDW peak was observed at $H \approx 0.28 \text{ r.l.u.}$, for $L \approx 1.25 \text{ r.l.u.}$ Due to the large X-ray wavelength at the Cu L -edge, only the first Brillouin zone was accessible, and hence $\mathbf{Q}$ is equivalent to the reduced wave vector $\mathbf{q}$.

Temperature dependence of CDW order. Figure 5 displays the temperature dependence of the CDW order peak for four of our samples ($T_c = 65 \text{ K}$, 69 K , 79 K , and 88 K). Measurements were typically carried out at temperatures that ranged from 12 K to $250\text{--}300 \text{ K}$. The intensity variation was carefully analyzed in order to estimate the onset temperature T_{CDW} . The intensity around Q_{CDW} decreases smoothly above T_c . The data obtained at one of the highest temperatures were used as reference “background” and subtracted from each low-temperature scan, and we checked that the intensity at Q_{CDW} does not vary further at higher temperatures. The resultant peaks were fitted with a Gaussian function, and the amplitude and full-width-at-half-maximum was extracted (Fig. 5). For the lowest-doped sample ($T_c = 55 \text{ K}$), the CDW signal was too small to allow this analysis. Instead, as shown in Fig. 7(a), the intensity in the range $H = 0.2 - 0.35 \text{ r.l.u.}$ was integrated at each temperature and the temperature at which the integrated intensity saturates was taken as the onset T_{CDW} . Figure 7(b) demonstrates that no intensity variation was observed in the nearly optimally-doped sample ($T_c = 94 \text{ K}$).

Calculation of reconstructed Fermi surface. The tight-binding FS calculations (Fig. 4) were performed for hole doping levels $0.07 \leq p \leq 0.11$. The hopping parameters that provide the best fit to dispersions from first-principles calculations were adopted from Ref. [42]: $(t, t', t'', t''') = (0.46, 0.105, 0.08, 0.02) \text{ eV}$. The doping dependence of the FS was simulated by adjusting the chemical potential so that the unreconstructed FS satisfies Luttinger’s sum rule and contains $1 + p$ holes, consistent with photoemission spectroscopy data [64]. Hence, $1 + p = 2A_{FS}/A_{BZ}$, where A_{FS} (A_{BZ}) is the area of the Fermi surface (Brillouin zone). In order to simulate the reconstructed FS, following Ref. [65], we constructed a 4 by 4 Hamiltonian and diagonalized it numerically at each point of reciprocal space, with a typical mesh of 10^6 points. Having set the band dispersion and wave vector to the experimentally determined values, the only adjustable parameter left for the calculations is the CDW potential Δ_{CDW} . We fixed the CDW potential to $\Delta_{CDW} = 50 \text{ meV}$ so that at $p = 0.09$ the size of the electron pocket that results from the FS reconstruction by the wave vector $q_{CDW} = 0.279(5) \text{ r.l.u.}$ yields the value of 3.06% of the Brillouin zone, consistent with experiment [20]. The CDW potential Δ_{CDW} was then kept constant for the calculation of the doping dependence, and the chemical potential was varied. The doping dependence of q_{CDW} employed in the calculations was obtained from the linear fit to the data in Fig. 3. After diagonalizing the Hamiltonian, four bands are found to cross the Fermi level, but only the band that corresponds to the electron pocket is displayed in Fig. 4 (in order to obtain only one band crossing the Fermi level (the electron pocket), one would have to start with a pseudogapped FS). The resulting FS, plotted in the reduced Brillouin zone in Fig. 4, is expected to undergo a Lifshitz transition from electron-like to hole-like Fermi pocket at $p \approx 10.5\%$. This result could in principle be verified experimentally by performing high-field/low-temperature transport measurements.

Modeling of the CDW correlation length. In order to better understand how i-O-induced disorder and inhomogeneity might affect the CDW correlations, we consider three simple models. The i-O density as a function of T_c was estimated from Refs. [27–29]. In the first model, we assume that CDW patches in the CuO_2 planes form in

regions between the i-O in the HgO_δ layers and that the size of the CDW patches is limited by the neighboring i-O (Fig. 8a). In this simple model, we randomly create circular CDW patches between the i-O, maximize their size, and numerically determine the probability $P(r)$ of finding a CDW patch with radius r . The scattering intensity from the CDW patches is given by

$$I(Q) \propto \sum_r P(r) \left| \int_{-r}^r dx \sqrt{r^2 - x^2} A e^{(iq_{CDW} \cdot x)} e^{-iQ \cdot x} \right|^2 \quad (1)$$

where A is the amplitude, q_{CDW} is the magnitude of the CDW wave vector, and Q is the magnitude of the momentum transfer. The calculations were performed on a 2000 x 2000 lattice of atoms for the doping levels $p = 0.063, 0.091, 0.107, 0.12$ and 0.142 . In the simulations, we assumed that A is independent of the radius. The size distribution of CDW patches results in a Gaussian line-shape of CDW peak (Fig. 8b). The correlation length is obtained by fitting a Gaussian to the the calculated CDW peak, in the same way as for the X-ray data. In this scenario, the calculated correlation lengths are significantly smaller than that obtained from the experiment, which indicates that it is unlikely that CDW correlations are destroyed by disorder associated with individual i-O. In the second model, we assume that the CDW patches develop around i-O and extend to the nearby i-O (Fig. 8c). The resultant correlation lengths are comparable to the first case. In the third model, we consider that the local environment may be significantly different from the typical situation (with zero or one i-O atom) when a CuO_2 plaquette is affected by two i-O, one in each of the two adjacent Hg-O layers. Such relatively rare unit cells with two i-O atoms may act as nucleation centers for CDW order and/or as strong pinning sites that lead to the destruction of CDW coherence. In this model, CDW patches extend from unit cells with two i-O atoms to neighboring CDW patches with two i-O atoms (Fig. 9). The phases of these CDW patches are uncorrelated, as the patches are pinned to different nucleation centers. This third model yields correlation lengths very close to the measured low-temperature values (Fig. 3a). A similar result is obtained by assuming that CDW patches are bound rather than pinned by such unit cells. Therefore, we cannot distinguish whether these sites assist the formation of CDW, or simply pin the CDW. We note that this third model is rather unique to Hg1201. For YBCO and other cuprates the CDW correlations may be affected by other types of disorder.

Demonstration of isotropic response. In Fig. 7(c), we demonstrate (for the sample with $T_c = 76$ K) the equivalence of scans along $[100]$ and $[010]$, as expected, given the tetragonal structure of Hg1201.

Search for CDW order in nearly optimally doped Hg1201. Based on (micro) X-ray diffraction measurements, CDW order has been reported for a nearly-optimally-doped sample of Hg1201 ($T_c = 95$ K), and it has been suggested that the CDW order competes with i-O order [51]. The reported doping level of this sample is well above the hole concentration up to which we detected the CDW order via resonant X-ray diffraction, a very sensitive probe of charge order. Moreover, the reported CDW correlation length exceeds 15 lattice constants at the onset temperature, and the reported wave vector of $q_{CDW} = 0.23$ r.l.u. is considerably lower than $q_{CDW} \approx 0.25$ r.l.u., the value predicted from linear extrapolation of our data in Fig. 3b. Since the reported charge order sets in at 240 K, approximately 50 K above $T^* \approx 190$ K [15], its origin is distinct from the CDW order reported here and in other cuprates. One possible explanation is that the observed peak originates from a spurious secondary phase present in the sample, and not from the CDW order. The data in Fig. 2a of Ref. [51] clearly show a secondary phase with larger lattice parameters, rotated by approximately 45 degrees with respect to the lattice of Hg1201. The coexistence of two phases would explain the apparent competition between the i-O order, a characteristic of Hg1201 near optimal doping, and the additional peak. Furthermore, the different lattice constants (and thermal expansion coefficients) of the two phases would explain the unusual temperature dependence of the observed peak (ξ/a increases above the onset temperature of 240 K). As detailed in Ref. [33], we were unable to detect the CDW order via hard (non-resonant) X-ray diffraction.

T_c (K)	p	ξ/a	q_{CDW} (r.l.u.)	T_{CDW} (K)	Comments
55	0.064	4.6(5)	0.292(7)	140(20)	very weak CDW
65	0.074	5.8(5)	0.297(5)	175(15)	
69	0.083	8.0(8)	0.281(8)	210(10)	
72	0.09	6.4(6)	0.276(6)	200(20)	Ref. [33]
74	0.094	6.0(5)	0.289(7)		
76	0.10	5.2(4)	0.270(5)		
79	0.105	4.6(3)	0.270(5)	175(10)	
88	0.115	4.8(7)	0.260(6)	140(50)	
94	0.126	-	-	-	no CDW

TABLE I: Hg1201 sample information. The critical temperature for each crystal was determined as the onset of the diamagnetic response in magnetic susceptibility measurements. The hole concentration was estimated from the T_c vs. p relationship provided in Ref. [37]. The CDW correlation length $\xi/a = (1/(\pi \cdot FWHM))$, was determined near T_c , from the FWHM of Gaussian fits to the data, as described in the text. Similarly, the wave vector was obtained from the center of the peak. T_{CDW} was estimated as described in the text.

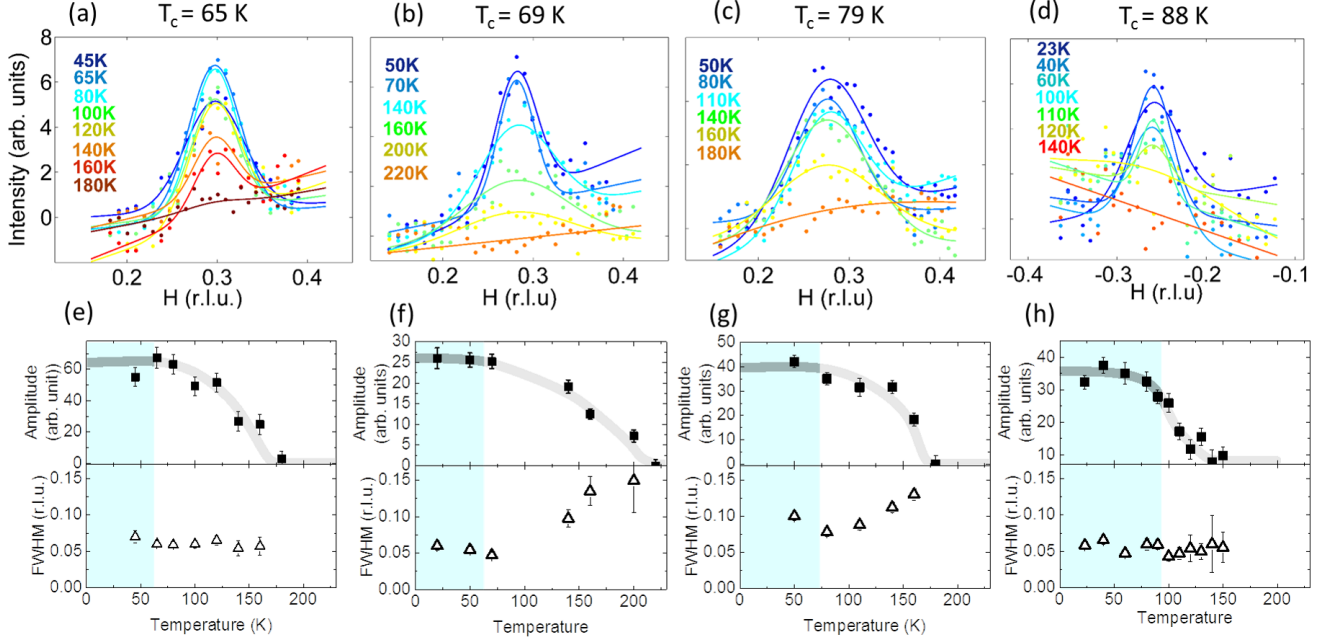


FIG. 5: (a-d) Temperature dependence of the background-subtracted CDW peak for four Hg1201 samples. The intensity at $H = q_{CDW}$ decreases above T_c and saturates at the onset temperature T_{CDW} (see also Fig. 6a). In order to obtain the most accurate temperature dependence of the CDW peak parameters, data obtained near this characteristic temperature were subtracted from the low-temperature scans (data collected at 200 K, 240 K, 200 K and 155 K were selected as the reference background for the samples with $T_c = 65$ K, 69 K, 79 K and 88 K, respectively). The solid lines are the result of subsequent Gaussian-function fits. (e-h) Temperature dependence of the peak amplitude and width (FWHM). Blue areas indicate the superconducting state for each sample. The thick gray lines are guides to the eye.

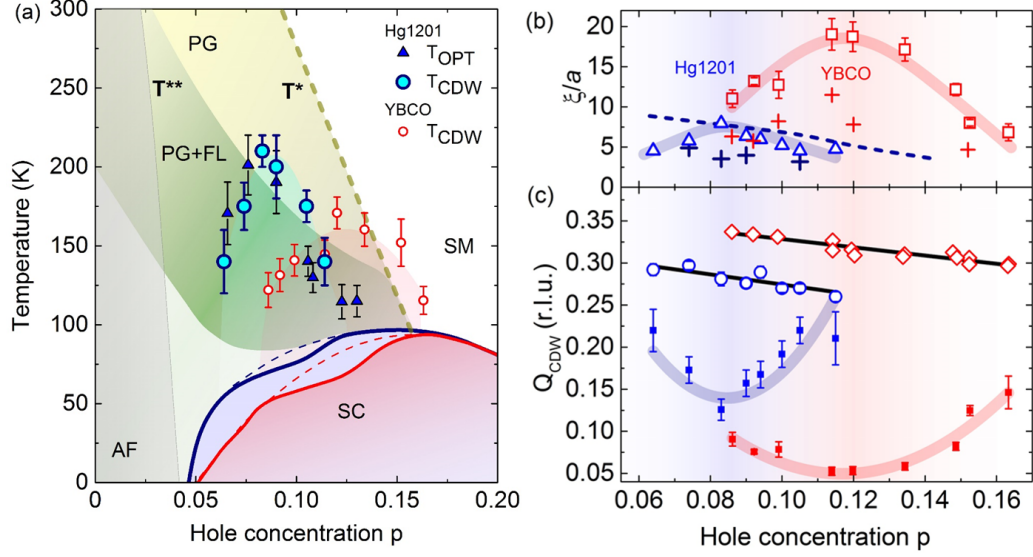


FIG. 6: (a) Combined phase diagram of Hg1201 and YBCO. The data for Hg1201 (blue) as in Fig. 1. Red circles mark the CDW onset T_{CDW} of YBCO [40] and the red solid line corresponds to the superconducting dome in YBCO [66]. For both compounds, the CDW order is coincident with the “plateau” in $T_c(p)$. (b) and (c) are analogous to Fig. 3: red crosses in (b) correspond to the CDW correlation length at 140 K, in the vicinity of T_{CDW} [40]. Blue and red squares in (c) correspond to the inverse correlation length in Hg1201 and YBCO, respectively. While in Hg1201 the CDW correlations vanish when ξ becomes comparable to the CDW modulation period, this limit is not reached in YBCO, possibly as a result of the lower defect density in the latter compound.

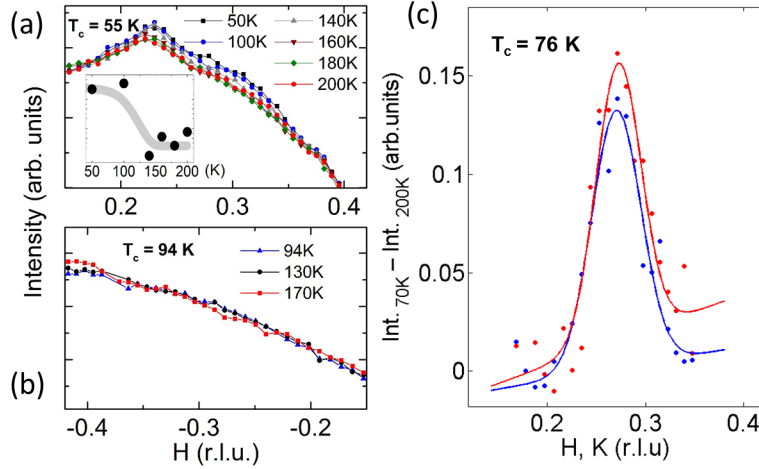


FIG. 7: Momentum scans across the CDW wave vector at the Cu L_3 resonance at various temperatures for two Hg1201 samples with (a) $T_c = 55$ K ($p = 0.064$) and (b) $T_c = 94$ K ($p = 0.126$). Due to the very low intensity of the CDW peak in the first sample, systematic subtraction of high-temperature “background” from the low-temperature scans did not result in a reliable estimate of the temperature dependence. Instead, the onset temperature of the CDW order was determined from the temperature dependence of the integrated intensity (between $H = 0.2$ and 0.35 r.l.u.), as shown in the inset. The onset temperature $T_{CDW} = 140(20)$ K is the temperature at which the integrated intensity saturates. No intensity change with temperature is observed in the nearly optimally-doped sample ($T_c = 94$ K), consistent with the absence of CDW order. (c) Background-subtracted momentum scan across q_{CDW} for a sample with $T_c = 76$ K ($p = 0.105$) along the equivalent directions [100] and [010]. The solid lines are Gaussian fits (with linear background) to the experimental data, yielding equivalent peak positions, amplitudes and widths, within the experimental uncertainty.

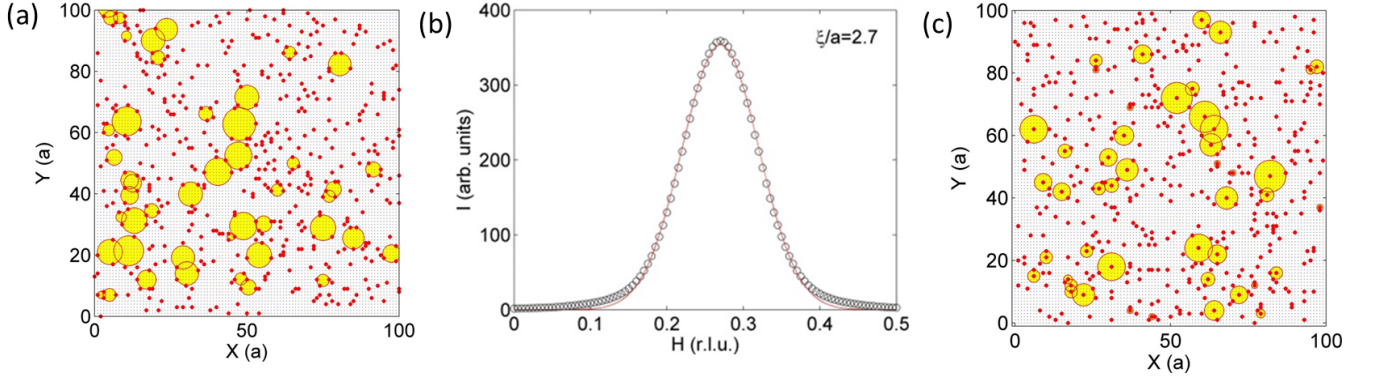


FIG. 8: (a) CDW patches (yellow circles) in the CuO_2 planes formed in regions between i-O atoms (red dots) in the HgO_δ layers. Displayed area: $(100a)^2$. The i-O density corresponds to $p = 0.063$ [27–29]. (b) CDW peak, calculated from the distribution of charge-order patches in (a); the correlation length $\xi/a = 2.7$ is obtained from a Gaussian fit. (c) Same as in (a), but CDW patches develop around i-O and extend to nearest-neighbor i-O.

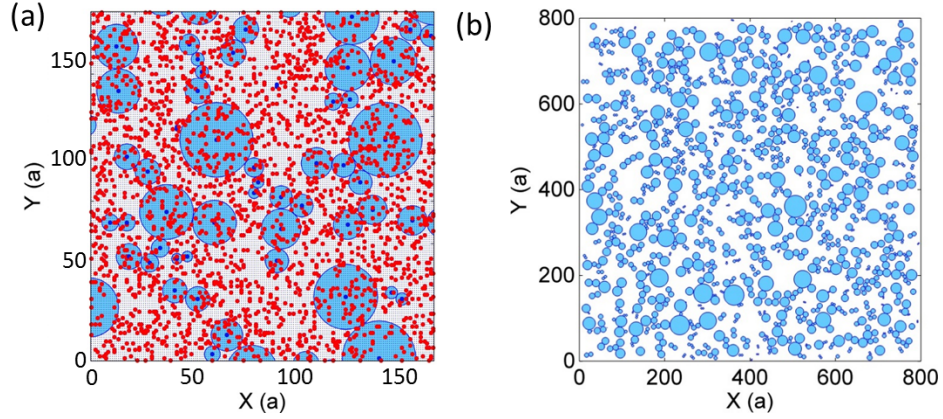


FIG. 9: (a) CDW patches (light blue circles) nucleated in relatively rare unit cells in which two i-O from two adjacent HgO_δ layers randomly overlap. The red dots indicate unit cells with one i-O, either in the top or the bottom HgO layer adjacent to the CuO_2 plaquette. The dark blue dots indicate unit cells with two i-O, each occupying one of the two adjacent HgO layers. The CDW patches extend to the closest doubly-occupied site. (b) as in (a), but on a larger scale for the better visualization of the CDW patch distribution.